


## Detail Gradation Statistical Summary Report

**Plant** 01 Atlanta Sand-Burke Pit  
**Product** 2 B-Burke Concrete Sand  
**Specification** 2 B Burke Concrete Sand  
**Period** 04/01/2025 - 04/30/2025

Sieve/Test	Tests	Average	Min	Max	Range	St Dev	Target	Specification	PWS
3/8" (9.5mm)	21	100	100	100	0	0.0		100-100	100.0
#4 (4.75mm)	21	100	100	100	0	0.0		95-100	100.0
#8 (2.36mm)	21	98	97	99	2	0.6			
#16 (1.18mm)	21	88	81	91	10	2.5		45-95	99.7
#30 (.6mm)	21	58	45	64	19	4.5			
#50 (.3mm)	21	19	11	22	11	2.9		8-30	100.0
#100 (.15mm)	21	2	1	2	1	0.5		0-10	100.0
Pan	21	0.0	0.0	0.0	0.0	0.00			
FM	21	2.358	2.227	2.640	0.413	0.0979			
SE	4	85.250	84.000	86.000	2.000	0.9574			
Wash Loss (#200/75um)	3	1.570	0.522	2.336	1.814	0.9393			

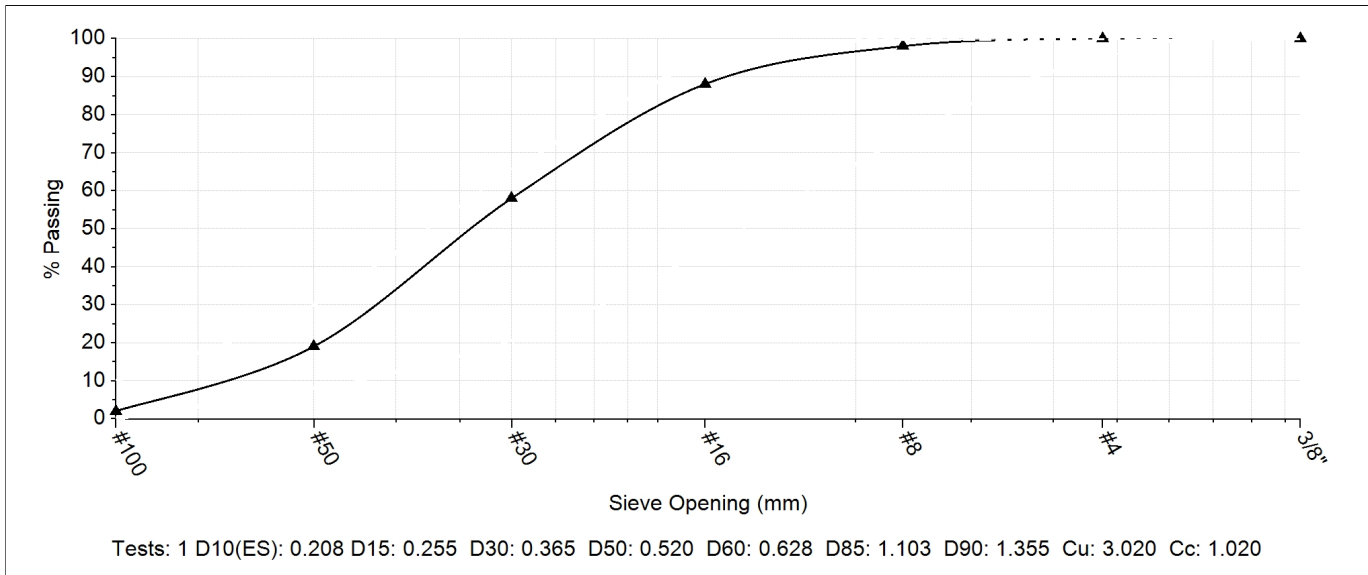

**Comments**

**Query**

Query Selections  
Date Created 05/02/2025  
Date Range 04/01/2025 - 04/30/2025  
Plant Burke Pit  
Sample Type Shipping