


Detail Gradation Statistical Summary Report

Plant 01 Atlanta Sand-Burke Pit
Product 2 B-Burke Concrete Sand
Specification 2 B Burke Concrete Sand
Period 06/01/2026 - 06/30/2026

Sieve/Test	Tests	Average	Min	Max	Range	St Dev	Target	Specification	PWS
3/8" (9.5mm)	22	100	100	100	0	0.0		100-100	100.0
#4 (4.75mm)	22	100	100	100	0	0.0		95-100	100.0
#8 (2.36mm)	22	98	95	99	4	1.0			
#16 (1.18mm)	22	87	74	90	16	3.4		45-95	99.1
#30 (.6mm)	22	53	35	61	26	5.7			
#50 (.3mm)	22	16	9	24	15	3.5		8-30	98.9
#100 (.15mm)	22	2	1	3	2	0.7		0-10	100.0
Pan	22	0.0	0.0	0.0	0.0	0.00			
FM	22	2.443	2.221	2.860	0.639	0.1338			
SE	4	91.250	87.000	95.000	8.000	3.5000			
Wash Loss (#200/75um)	4	1.209	0.983	1.572	0.589	0.2600			

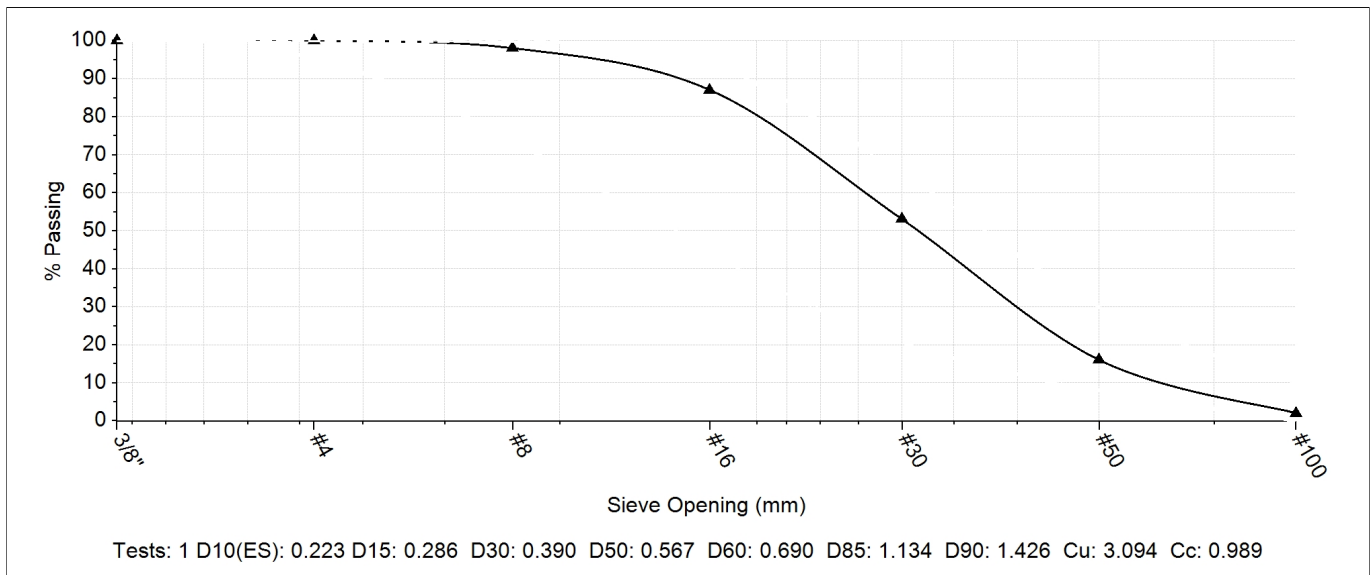

Comments**Query**

Query Selections

Date Created 07/01/2026

Date Range 06/01/2026 - 06/30/2026

Plant Burke Pit

Sample Type Shipping