


## Detail Gradation Statistical Summary Report

**Plant** 01 Atlanta Sand-Burke Pit  
**Product** 2 B-Burke Concrete Sand  
**Specification** 2 B Burke Concrete Sand  
**Period** 07/01/2026 - 07/31/2026

| Sieve/Test            | Tests | Average | Min    | Max    | Range | St Dev | Target | Specification | PWS   |
|-----------------------|-------|---------|--------|--------|-------|--------|--------|---------------|-------|
| 3/8" (9.5mm)          | 22    | 100     | 100    | 100    | 0     | 0.0    |        | 100-100       | 100.0 |
| #4 (4.75mm)           | 22    | 100     | 100    | 100    | 0     | 0.0    |        | 95-100        | 100.0 |
| #8 (2.36mm)           | 22    | 98      | 97     | 99     | 2     | 0.6    |        |               |       |
| #16 (1.18mm)          | 22    | 86      | 79     | 93     | 14    | 3.5    |        | 45-95         | 99.5  |
| #30 (.6mm)            | 22    | 54      | 39     | 74     | 35    | 7.9    |        |               |       |
| #50 (.3mm)            | 22    | 16      | 8      | 25     | 17    | 3.9    |        | 8-30          | 98.0  |
| #100 (.15mm)          | 22    | 2       | 0      | 5      | 5     | 1.1    |        | 0-10          | 100.0 |
| Pan                   | 22    | 0.0     | 0.0    | 0.0    | 0.0   | 0.00   |        |               |       |
| FM                    | 22    | 2.434   | 2.096  | 2.773  | 0.677 | 0.1594 |        |               |       |
| SE                    | 5     | 90.600  | 88.000 | 94.000 | 6.000 | 2.1909 |        |               |       |
| Wash Loss (#200/75um) | 5     | 1.141   | 0.844  | 1.459  | 0.615 | 0.2540 |        |               |       |

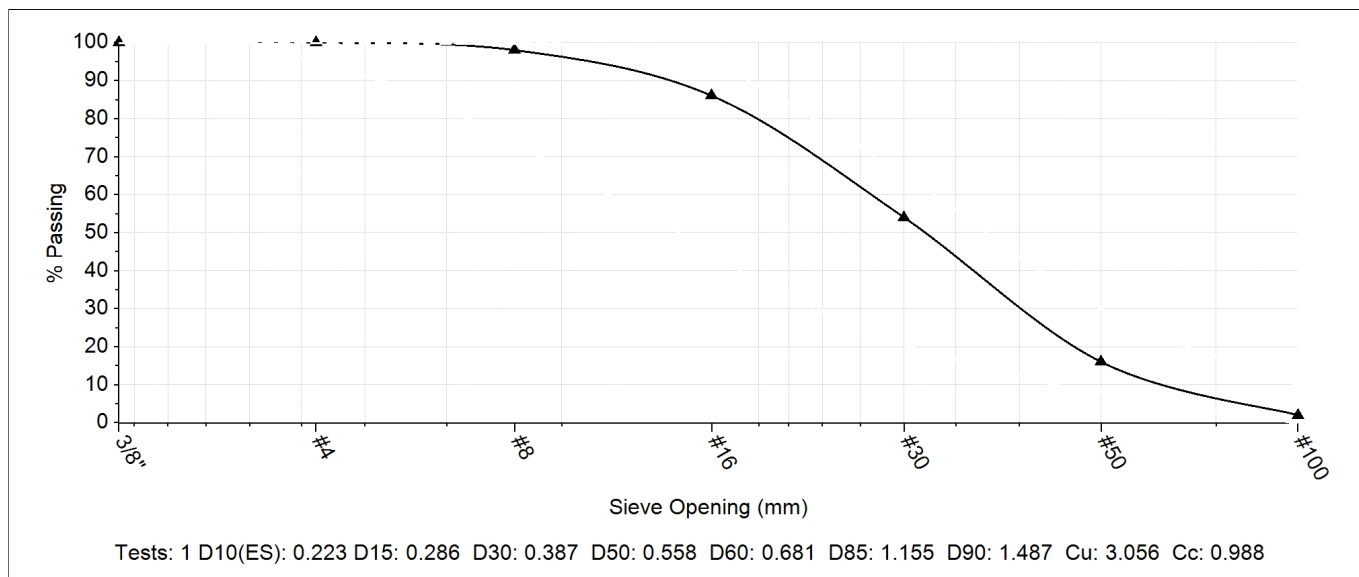

**Comments****Query**

Query Selections

Date Created 08/03/2026

Date Range 07/01/2026 - 07/31/2026

Plant Burke Pit

Sample Type Shipping

Sample Method Load-Out Face